

DAW Nordic AB
Martina Claeson
Box 36115
400 13 GÖTEBORG

Emission measurements according to M1

(3 appendices)

Assignment

Emission measurement according to “M1 Emission Classification of Building Materials: Protocol for Chemical and Sensory Testing of Building Materials”, ver 5.7.2017, after 28 days of conditioning regarding volatile organic compounds, carcinogenic compounds (EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), formaldehyde, ammonia and sensory acceptability.

For evaluation of test results the principle of shared risk is applied, i.e. for a max limit (\leq) a result \leq the limit complies and a results $>$ the limit does not comply (ILAC G8 section 2.7).

Product/test specimen

Table 1.

Product type:	Interior wall paint
Product name:	Supertäck 7 Plus Bas A
Batch No:	2437014483
Manufacturing date:	2017-06-14
Packaging:	1 L can
Arrived at SP:	2017-08-25
Test specimen preparation:	Wall scenario, density of 1.247 g/L and spreading rate of 8 m ² /L are used for the testing. Chemical testing: The paint was applied with roller on two glass plates of 0.25 x 0.40 m, total surface area of 0.20 m ² . Applied amount was 15.4 g per plate. Sensory testing: The paint was applied with roller on eight glass plates of 0.50 x 0.40 m and one of 0.25 x 0.40 m, total surface area of 1.7 m ² . Mean applied amount per large plate was 31.2 g.
Deviation from protocol:	No
Test period started, date:	2017-08-29
Conditions during ageing:	23 ± 2 °C, 50 ± 5 % RH
Emission samplings, date:	2017-09-26

RISE Research Institutes of Sweden AB

Postal address	Office location	Phone / Fax / E-mail
Box 857	Brinellgatan 4	+46 10 516 50 00
SE-501 15 BORÅS	SE-504 62 BORÅS	+46 33 13 55 02
Sweden		info@ri.se

Laboratories are accredited by the Swedish Board for Accreditation and Conformity Assessment (SWEDAC) under the terms of Swedish legislation. This report may not be reproduced other than in full, except with the prior written approval of the issuing laboratory.

Methods

The specimens were conditioned outside the testing chambers in separate conditioning containers (with air velocity of ca 0.2 m/s) in a room with controlled climate conditions of 23 ± 2 °C and 50 ± 5 % RH. The specimens were placed in the chambers four days before the measurements of the chemical emission and two days before the sensory evaluation.

Table 2.
Chamber conditions of the test of chemical emissions

Test chamber volume:	0.25 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Air exchange rate:	0.5 h ⁻¹
Air velocity at specimen surface:	0.1 – 0.3 m/s
Area of sample:	0.20 m ²
Area specific air flow rate:	0.625 m ³ /m ² h

Table 3.
Chamber conditions of the test of sensory acceptability

Test chamber volume:	1.0 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Supply air flow rate:	0.9 l/s = 3.24 m ³ /h
Area of sample:	1.7 m ²

Table 4.
Emission sampling and analytical methods

Test	Sampling method	Adsorbent	Sampling volume (litre)	Analysis method / Quantification	Detection limit
VOC	ISO 16000-9:2006 ¹	Tenax TA	2 - 9	RISE 0601 ² / FID quantification	1 µg/m ³
Formaldehyde	ISO 16000-9:2006 ¹	DNPH	30 - 50	RISE 2303 ³ /HPLC-UV	0.03 µg/sampler
Ammonia	ISO 16000-9:2006 ¹	Treated silica gel	310 - 390	Liquid chromatograph with conductivity detector ⁴	0.9 µg/sampler
Sensory evaluation	ISO 16000-28:2012 ⁵	--	--	Acceptability, Untrained panel of min 15 persons	--

¹⁾ In accordance with ISO 16000-9:2006 and M1 protocol.

²⁾ In accordance with ISO 16000-6:2011 and M1 protocol.

³⁾ In accordance with ISO 16000-3:2001.

⁴⁾ The determinations of the sampled silica gel tubes were done by Sahlgrenska Universitetssjukhuset, Miljökemiska laboratoriet, Göteborg, not accredited method.

⁵⁾ In accordance with M1 protocol, not accredited method.

Tenax TA was used as adsorption medium for VOC. The tubes were thermally desorbed and analysed in accordance to RISE method 0601, similar to ISO 16000-6:2011 (Determination of volatile organic compounds in indoor and test chamber air by active sampling on Tenax TA sorbent, thermal desorption and gas chromatography using MS/FID). This means an analysis in a gas chromatograph and detection with a flame ionisation detector (FID) and mass selective detector (MS). The FID signals are used for compound quantification. The TVOC is quantified

as toluene equivalents. The mass selective detector is used for identification of compounds. The capillary column used is coated with 5% phenyl/ 95 % methylpolysiloxane. Tenax TA was also used as adsorption medium for testing of volatile carcinogenic compounds, according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), (exclusive formaldehyde), 0.001 mg/m³ and above.

The sampling of formaldehyde was carried out with DNPH samplers. The samplers were analysed according to RISE method 2302, similar to ISO 16000-3:2011(Indoor air--Part 3: Determination of formaldehyde and other carbonyl compounds – Active sampling method), which means analysis on a liquid chromatograph with absorbance detector.

The sampling of ammonium was carried out with silicagel treated adsorbent tubes and analysis on a liquid chromatograph with conductivity detector.

Minimum two subsequent samples were taken for the VOC determination, for the formaldehyde and for the ammonia respectively.

Results

The results of the chemical testing are expressed as area specific emission rates and as concentrations in a model room. The model room has a base area of 3 m x 4 m and a height of 2.5 m, with an air exchange rate of 0.5 h⁻¹. The wall area is 31.4 m², floor area is 12 m², small area, like a door, is 1.6 m² and very small area, like sealant, is 0.2 m². Wall area is used for the calculation of the concentrations.

Calculation of the concentration from the emission rate:

$$Conc = \frac{SER_A \times A}{n \times V}$$

Conc = concentration of a VOC in the model room, in µg/m³
 SER_a = area specific emission rate, in µg/m²h
 A = area of sample, in m²
 n = air exchange rate, in changes per hour
 V = volume of the model room, in m³

Table 5.

Results of the chemical testing of the sample **Supertäck 7 Plus Bas A** after 28 days

Compound	Concentration in model room mg/m ³	Emission rate mg/m ² h	Criteria M1 mg/m ² h
TVOC ⁶	0.27	0.13	< 0.2
Carcinogens	< 0.001	< 0.001	< 0.005
Formaldehyde	< 0.001	< 0.001	< 0.05
Ammonia ⁷	< 0.003	< 0.002	< 0.03

⁶⁾The TVOC is the sum of the individual concentration $\geq 5 \mu\text{g}/\text{m}^3$ in model room.

⁷⁾ Not accredited method.

Test report from Sahlgrenska Universitetssjukhuset: test report 2017:26 dated 2017-10-25.

Table 6.

Results of the sensory acceptability evaluation of the sample **Supertäck 7 Plus Bas A**, after 28 days

Evaluator	Sensory evaluation	Criteria M1
1	1.0	
2	0.75	
3	0.95	
4	1.0	
5	0.90	
6	0.95	
7	0.95	
8	0.90	
9	0.40	
10	0.35	
11	0.95	
12	1.0	
13	0.95	
14	1.0	
15	0.95	
Arithmetic mean of acceptability ⁸	0.87	≥ + 0.0
Standard deviation	0.21	
90 % confidence interval of arithmetic mean	0.10	

⁸⁾ Not accredited method.

The empty sensory test chamber acceptability was determined 2017-09-22. The mean acceptability vote of the empty chamber was ≥ 0.8.

Interpretation of the results

The tested product **Supertäck 7 Plus Bas A** complies with all the requirements of M1 for the tested parameters.

Detailed results

Table 7.

Detailed results (emission rates) of the chemical testing after 28 days

Sample	TVOC (mg/m ² h) as toluene equivalents between C ₆ -C ₁₆	Formaldehyde (mg/m ² h)	Ammonia (mg/m ² h)	Carcinogens (mg/m ² h) between C ₆ -C ₁₆
1	0.13	< 0.001	< 0.002	< 0.001
2	0.13	< 0.001	< 0.001	< 0.001

Table 8.
Single VOCs above 5 µg/m³ in the model room (wall scenario)

Single VOCs	CAS number	Retention time (min)	ID ⁹	Concentration (µg/m ³)	
				Sample 1	Sample 2
Single VOCs C₆-C₁₆:	--	6.2 - 37.9			
Probably: Tripropylene glycol monomethyl ether	20324-33-8	35.4-36.0	B	270	280
TVOC	--	6.2 - 37.9	B	270	280
Volatile Carcinogens¹⁰		6.2 – 37.9			
No substances detected	--	--	B	< 1	< 1
Single VOC outside C₆ – C₁₆:					
VVOC (< C ₆) ¹¹		4.8 – 6.2			
No single VVOC detected	--	--	B	< 5	< 5
SVOC (C ₁₆ – C ₂₂) ¹²		37.9 - 50.0			
No single SVOC detected	--	--	B	< 5	< 5

⁹⁾ ID: A = quantified compound specific, B = quantified as toluene-equivalent

¹⁰⁾ Volatile carcinogens = VOCs according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B

¹¹⁾ VVOC = very volatile organic compounds, as defined in ISO 16000-6 (not accredited)

¹²⁾ SVOC = semi-volatile organic compounds, as defined in ISO 16000-6 (not accredited)

TVOC is the sum of all individual substances with concentrations $\geq 5 \mu\text{g}/\text{m}^3$ (in toluene equivalents). Level of identification of compounds is 100 % for all compounds $\geq 5 \mu\text{g}/\text{m}^3$.

The detected compound does not have EU-LCI values.

Measurements uncertainty

The expanded measurement uncertainty of VOC result is 15 % (rel) and formaldehyde is 30 % (rel). The expanded measurement uncertainty for ammonia is 14 % (rel) according to the test report from Sahlgrenska Universitetssjukhuset.

See Appendix 1 for a gas chromatogram from the VOC determination and Appendix 2 for a photo of a the test specimen. Appendix 3 is the Sampling report received from the customer.

RISE Research Institutes of Sweden AB Chemistry, Materials and Surfaces - Chemistry

Performed by

Examined by

Maria Rådemar

Tove Malin

Appendices


1. Gas Chromatogram
2. Photo of the test specimen
3. Sampling report

Appendix 1

Gas chromatogram

Sample: **S Supertäck 7 Plus Bas A**, after 28 days
(sampled volume: 6 litres):

Abundance

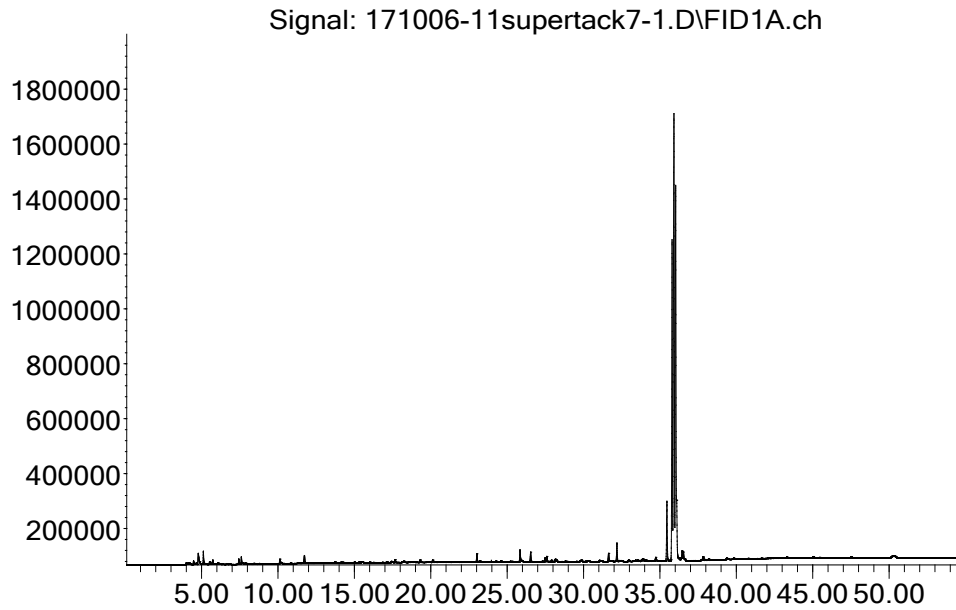

TVOC between C_6 and C_{16} , means compounds eluting between 6.2 and 37.9 minutes.

Appendix 2

Photo of the test specimen**Supertäck 7 Plus Bas A**

Appendix 3

Sampling Report (paints etc)

Sampler (Name, Company, contact info): Martina Claeson DAW Nordic AB Box 36115 Göteborg , Sweden		Manufacturer of the product (Company, address): DAW Nordic AB Box 36115 40013 Göteborg, Sweden	
Name of product: Supertäck 7 Plus Bas A		Product category according to EN 16402:2013, clause 5: Interior wall paint	
Manufacturing Date: 2017-06-14		Batch No: 2437014483	
Amount of material sampled: 0,95 L		Density (g/L): 1,247	
Solid content (vol %): 40		Spreading rate (m²/L): 8-10	
Sample is taken from: Production line <input type="checkbox"/> Stock / Storage <input type="checkbox"/> Miscellaneous <input type="checkbox"/> -where, specify:		How was the product stored before sampling? In the warehouse	
If a sub-sample was collected from a larger material amount, describe how the sub-sample was taken:		Packing material: Steel can	
Remarks:			
Confirmation: I hereby confirm that the sample was selected, taken and packed in accordance with this protocol.			
Date of sampling: 2016-08-24		Signature: 